

# ASSESSMENT AND INFLUENCE ON PROPERTIES OF M<sub>40</sub> GRADE OF CONCRETE BY USING COLLOIDAL NANO SILICA

Deepak Ranjan<sup>1</sup>, Prof. Rahul Sharma<sup>2</sup>

<sup>1</sup>Research Scholar

<sup>2</sup>Asst. Professor

Department of Civil Engineering

Prashanti Institute Of Science and Technology, Ujjain(M.P.)

## ABSTRACT

*This is the aeon of reformation and it can be more reform by using eco-friendly construction material i.e. Colloidal Nano-silica (in order to intensify the compressive strength of concrete as well as concurrently devaluate in the creep and shrinkage of concrete). In this study the strength parameters of concrete of M-40 grade can be analyzed by replacing cement by affix dissimilar percentages of Colloidal Nano- Silica 0%, 5% and 10% of by weight of cement of cement in concrete. Strength Properties studies involve compressive strength, flexural strength. All the mixes were cured and tested with the compressive strength test as well as flexural strength test for 7 days, 14 days and 28days. The results acquired from tests is to be compared with the traditional concrete mix. The study shows that the use of waste material like Nano-silica liquid in concrete is feasible.*

**Keywords:** Colloidal Nano-Silica Liquid (NS), Compressive strength (CS), Flexural strength (FS)

## 1. INTRODUCTION

Now a days, infrastructure projects are increased at a very swift rate. Which leads to the production of cement at incredible rate. A huge amount of energy is consumes in the production of cement, that releases the magnanimous amount of CO<sub>2</sub> as a chief sources of air pollution. For the production of ordinary Portland cement it consumes natural resources like limestone, as well as Argillaceous product and there is a instant need to economize the use of cement. Large amount of solid waste is produced in forms of silica fume and recron fiber.. Some test program has been conduct which shows increased in compressive strength of concrete by adding Nano-silica liquid in it The addition of Nano-silica Liquid in concrete is efficient for improving its compressive strength simultaneously able to enhance its Flexural Strength as well as helps in reducing the drying shrinkage in concrete and improving the abrasion resistance. Nano-Concrete also improve the bond strength with the reinforcing steel, and reducing the permeability in concrete. For workability and flexural strength of fiber reinforced Nano-silica concrete, nano- silica content used were 0%, 5% and 10% by replacement of weight of cement. The aim of this study is to evaluate the feasibility of using waste material like Nano-silica . In this Research work, a suitable mix proportion with and Nano-silica in concrete that elevates the strength. Nano- silica liquid sss are one of the materials that are considered as a waste material which could have a promising future in construction industry. Pietro Di Maida (2017) Nanosilica-based treatment by means of the sol-gel process was successfully conducted on macro-synthetic PP fibres in order to improve the interaction area at the interface between the synthetic fibres and the concrete matrix. Rahul Dogra and Ankit (2016) his study

result shows that the partial replacement of 10% silica fume with cement can giving most extreme conceivable compressive strength with polypropylene fiber. R. Karthi & Dr. P. Chandrasekaran (2014) Concluded that the Compressive strength of the silica fume concrete with polypropylene fibers has increased by 10.63%, then Conventional concrete.

## 2. RESEARCH METHODOLOGY

In the current exploration work concrete has been mostly supplanted by Colloidal Nano-Silica Liquid in M40 Grade of cement. The substitution levels are 0%, 5% and 10% by weight of concrete. The properties researched are functionality, compressive quality, flexural quality. The examples of standard shapes (150mm×150×mm×150mm), and standard shafts (150mm×150mm×700mm) were projected from various blends having various substitutions levels of Colloidal Nano-silica. The examples were restored in water for required time.

## 3. MATERIAL & THEIR PROPERTIES

### Cement

An OPC 43 grade Ultra Tech Cement was used in this study. The physical properties were found using respective IS codes. The properties are given in table below:-

**Table1: - Properties of Cement**

S.NO	SPECIFICATION	VALUES
1	Specific Gravity	3.13
2	Standard Consistency	32%
3	Initial Setting Time	30 min
4	Final Setting Time	600 min

### 3.2 Fine Aggregate

The sand used in this research work acquired from natural river passing through 4.75mm I.S.Sieve The properties of sand obtained using respective codes are given in table below. shown in Table-2

**Table2:- Properties of Fine Aggregate**

S.NO	SPECIFICATION	VALUES
1	Specific Gravity	2.63
2	Fineness Modulus	2.93
3	Bulk Density(Kg/m <sup>3</sup> )	1645
4	Water Absorption(%)	0.94

### 3.3 Coarse Aggregate

In this research work locally available crushed aggregate of sizes 20mm and 10mm were used. The aggregates were tested and following results were obtained, shown in Table 3

**Table: 3-Properties of Coarse aggregate**

S.NO	SPECIFICATION	VALUES
1	Specific Gravity	2.66
2	Fineness Modulus	6.75
3	Bulk Density(Kg/m <sup>3</sup> )	1585
4	Water Absorption(%)	0.64
5	Impact value	21.10
6	Abrasion Value	24.97

### 3.4 Colloidal Nano-Silica

Nano-SiO<sub>2</sub> has been found to improve concrete workability and strength, to increase resistance to water penetration, and to help control the leaching of calcium, which is closely associated with various types of concrete degradation. Nano-SiO<sub>2</sub> was found to be more efficient in enhancing strength than silica fume. The raw material of Nano-silica is derived from monomeric C<sub>3</sub>H<sub>6</sub> which is purely hydrocarbon.

**Table: 4- Properties of Colloidal Nano-Silica Liquid**

S.NO	SPECIFICATION	VALUES
1	Specific Gravity	2.20
2	Fineness Modulus	2.55
3	Bulk Density(Kg/m <sup>3</sup> )	1310
4	Moisture(%)	<1.5
5	Loss On Ignition	<1.5
6	Surface Area(m <sup>2</sup> /g)	2000

### 3.5 Water

Potable water available from nature sources free from deleterious materials was used for mixing as well as for curing of all the mixes tried in this investigation.

## 4. MIX DESIGN

The mix design was done using IS: 10262-2009 and IS: 456--2000. The calculated proportion for 1 m<sup>3</sup> is given below:-

**Table-6 Mix Proportion for M 30 Concrete**

Mix	Raw Material				
	Replacement Of Cement(%)	Cement	Sand	Coarse Aggregate	Colloidal Nano-Silica(%)
CC	00	447	769	1044	00
MD <sub>1</sub>	5	424	769	1044	5
MD <sub>2</sub>	10	402	769	1044	10

## 5. RESULTS

### 5.1 Workability-

The slump test were conducted according to May be: 1199-1959 to determine the usefulness of fresh concrete blend having different percentage of Colloidal Nano-Silica as 0%, 5%, 10% by weight of concrete. During the whole research work the water to cement proportion was kept 0.44. From the exploration, it was concluded that adding Colloidal Nano-Silica. The whole research work the water to cement proportion was kept 0.44. From the examination, it was concluded that adding Nano-Silica in concrete increases the functionality in concrete blend.

### 5.2 Compressive Strength-

Cube specimen of concrete were prepared incorporated with 0%, 5%, 10%, of Colloidal Nano-Silica of

size 150x150x150 mm, cured and tested for 7, 14 and 28 days as per IS: 516-1959. The testing results were obtained are shown in Table 7 and graphical represented shown in Figure 1. From the above test results, it can be concluded that the highest compressive strength was achieved by replacement 10% of Cement with 10% of Colloidal Nano-Silica in it and it is found out about  $55.8\text{N/mm}^2$  compared with  $48.6\text{N/mm}^2$  for the control mix after 28 days of curing.

**Table -7 Compressive Strength Test**

Samples	Replacement of Cement(%)		Compressive Strength (N/mm <sup>2</sup> )		
	Cement	Colloidal Nano-Silica	7 Days	14 Days	28 Days
CC	100	00	28.9	38.1	48.6
MD <sub>1</sub>	95	5	30.9	43.2	52.9
MD <sub>2</sub>	90	10	31.2	46.5	55.8

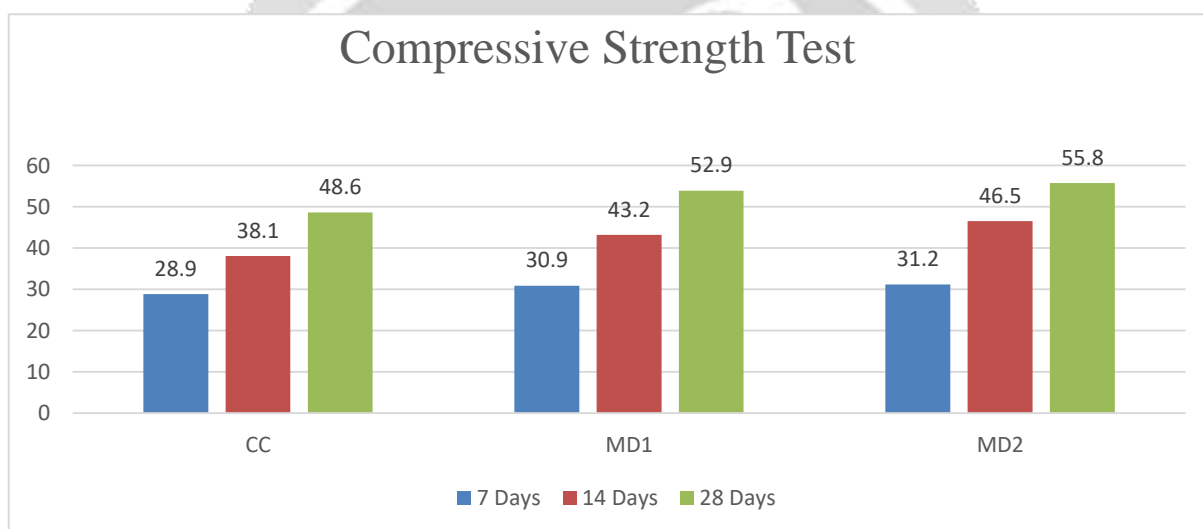


Fig 1. Compressive Strength Test

### 5.3 Flexural Strength

Standard beam of size 15cm x 15cm x 70cm were casted, cured, tested under one point loading to study the flexural strength of concrete is carried out as per 516:1959. Cubes were prepared, cured and tested for 7, 14 and 28 days.

After curing the test results were obtained are shown in Table 8 and graphical represented shown in Figure 2. From the above test results, it can be concluded that the flexural strength of concrete with 10% replacement of cement with Colloidal Nano-Silica Liquid elevates the strength of concrete mix. Highest flexural strength was achieved by replacement 10% of Cement by 10% of Colloidal Nano-Silica in it and it is found that strength about  $7.1\text{N/mm}^2$  as compared to  $6.1\text{N/mm}^2$  for the control mix after 28 days of curing..

**Table-8 Flexural Strength Of Concrete**

Samples	Replacement of Cement(%)	Flexural Strength (N/mm <sup>2</sup> )
---------	--------------------------	--

	Cement	Nano-SilicaLiquid	7 Days	14 Days	28 Days
CC	100	00	4.4	5.2	6.1
MD <sub>1</sub>	95	5	4.9	5.6	6.8
MD <sub>2</sub>	90	10	5.1	5.8	7.1

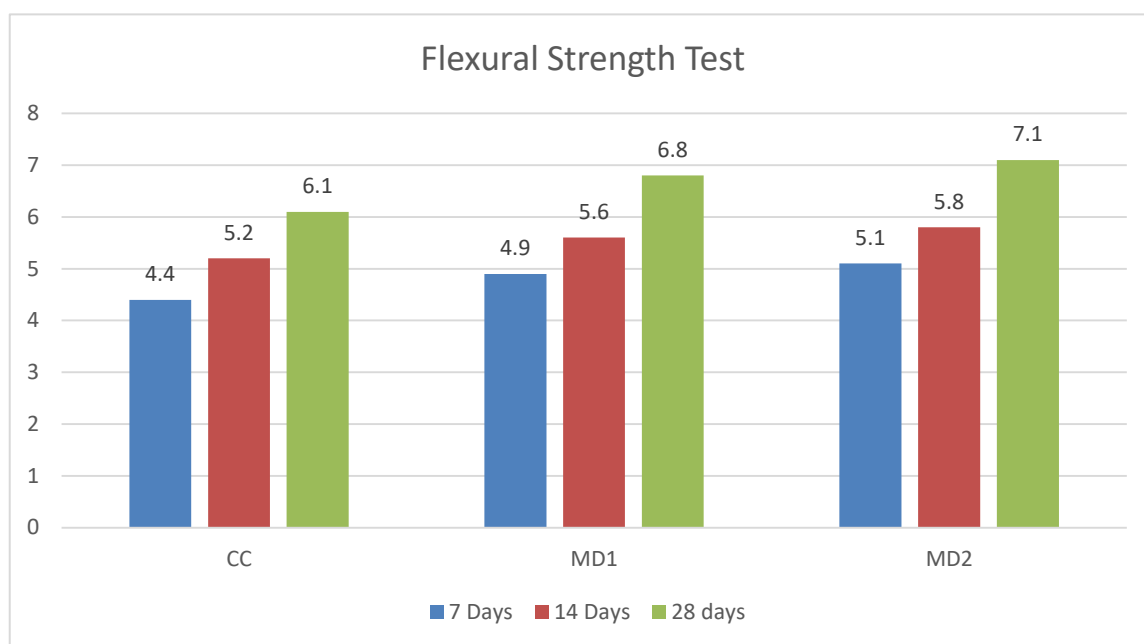


Fig 2- Flexural Strength Test

## 6. CONCLUSION

From the experimental investigation carried out for present dissertation work, following salient conclusion can be drawn.

- ❖ This case study clearly shows that Compressive strength of the Nano-concrete has increased by **12.90%**, then Conventional concrete as well as the flexural strength increased by **14.08%**
- ❖ Maximum Substitution of Colloidal Nano-Silica Liquid is 10% so as to Maximize the quality.
- ❖ Addition of Colloidal Nano-silica improves the tension stiffening effect considerably and this increases the bond stress of reinforced bars in composite reinforced concrete than in plane concrete.
- ❖ At 28 days the compressive strength of concrete increases. The strength decreases when we add beyond 10% of Nano-Silica Liquid.

## 7. FUTURE WORK

From the experimental study it is clear indicated that using Colloidal Nano-silica in concrete elevates the strength parameters. Following parameters will be study in future work-

- ❖ Study should be done in proportion zone i.e how much cement can be replaced by adding Nano-Silica Liquid
- ❖ More efforts can be done on analysing the flexural behaviour of Nano-Concrete.
- ❖ Trial of concrete mix should be done with Copper Slag.
- ❖ More efforts can be done on analysing the flexural behaviour of Nano-Concrete.
- ❖ Trial of concrete mix should be done with seawater.
- ❖ Better admixture should be searched in order to enhance the strength

## REFERENCES

1. Dr. A. Thirumurugan(2020) EXPERIMENTAL INVESTIGATION OF HYBRID FIBER CONCRETE WITH NANOSILICA International Journal of Scientific & Engineering Research Volume 11, Issue 3, March-2020 ISSN 2229- 5518
2. Chenglong Zhuang and Yu Chen(2019) The effect of nano-SiO<sub>2</sub> on concrete properties: a review <https://www.degruyter.com/document/doi/10.1515/ntrev-2019-0050/html>
3. N.Mohanraj, E.Arundhava Priya, A.Gopalan(2019) International Journal of Innovative Technology and Exploring Engineering (IJITEE) ISSN: 2278-3075, Volume8 Issue-6S, April 2019 “Experimental Study on Hybrid Concrete Using Steel Fiber Polypropylene Fiber and Silica Fume”
4. Swapnil Gupta(2018) “Assessment-of-influence-on-mechanical-properties-of-m40-grade-of-concrete-by-using-polypropylene-fiber-and-nano-silica-liquid”
5. Akash Kumar, Gurpreet Singh(2018) Effect of Nano Silica on the Fresh and Hardened Properties of Cement Mortar” International Journal of Applied Engineering Research ISSN 0973-4562 Volume 13, Number 13 (2018) pp. 11183-11188
6. Irfaz ur Rahman Najar, Jagdish Chand kambooj (2018), Combion effect of Silica fume, Fly ash and steel fiber on reinforced concrete
7. Toutanji HA. Properties of polypropylene fiber reinforced silica fume expansive-cement concrete Department of Civil and Environmental Engineering, University of Alabama in Huntsville, AL 35899,USA.
8. Priti A. Patel, Dr. Atul K. Desai., and Dr. Jatin A. Desai, Evaluation of Engineering Properties for Polypropylene Fiber Reinforced Concrete, International Journal of Advanced Engineering Technology,3(1), January-March 2012, pp. 42-45.
9. Sobolev, k., (2004). “The development of a new method for proportioning of high performance concrete mixtures.” Cement and Concrete Composites, 26 (2004) Pp 901-907.
10. Ajay, V., Chandak, R., and Yadav, R.K., . “Effect of micro silica on the strength of concrete with ordinary Portland cement” Research journal of Engineering Science ISSN 2278-9472 vol.1 (3), 1-4, sept (2012).
11. Hootan.R.D., (1993). “Influence of silica fume replacement of cement on physical properties and resistance to sulphate attack, freezing and thawing, and alkali-silica reactivity”. ACI Materials Journal, 90(2) Pp 143-152.

12. Rao, G.A., (2003). "Investigations on the performance of silica fume incorporated cement pastes and mortars". Cement and Concrete journal, 33(11). Pp 1765-1770.
13. Alshamsi, A.M., Sabouni, A.R., Bushlaibi, A.H., (1993). "Influence of set retarding super plasticizers and micro silica on setting time of pastes at various temperatures". Cement Concrete journal Res. 23(3). Pp 592-598
14. Cohen, M. D., Bentur, A., (1988). "Durability of Portland silica fume pastes in magnesium and sodium sulphate solutions". ACI Materials Journal. 85(3). Pp 148-157.
15. Kumar, D., and Roy, S., "Effect of Partial Replacement of Cement by Silica Fume on Hardened Concrete". International journal of engineering Technology and Advanced Engineering (ISSN 2250- 2459, volume 2, issue 8, August 2012)
16. IS 456-Part 4-2000, "Indian Standard Code of Practice for plain and reinforced concrete" .BIS, New Delhi.
17. IS: 383-Part-2-1970, "Indian standard specification for coarse and Fine aggregates from natural source for concrete. BIS, New Delhi
18. IS 2386-1963, "Indian Standard Methods of tests for aggregate" BIS, New Delhi.
19. IS: 10262-1982, "Recommended guidelines for concrete mix design," BIS, New Delhi.
20. IS: 4031-PART 5-1988, "Methods of Physical Test for Hydraulic Cement". BIS, New Delhi.
21. IS: 516-1959, "Methods of test for strength of concrete.
22. ASTM C496. "Standard method for determination of splitting tensile strength of concrete cylinders".
23. IS: 4031-Part 11-1988, "Methods of Physical Tests for Hydraulic Cement". BIS, New Delhi.
24. Bentur, A., Mindess S., and Skalny, J., 1989, „Reinforcement of normal and high strength concrete with fibrillated polypropylene“, fiber reinforced cements and concretes recent developments edited by R.N.Swamy, ISBN 1-18166-415-7, pp.229-239.
25. Priti A. Patel, Dr. Atul K. Desai., and Dr. Jatin A. Desai, Evaluation of Engineering Properties for Polypropylene Fiber Reinforced Concrete, International Journal of Advanced Engineering Technology, 3(1), January-March 2012, pp. 42-45.
26. Neel Shah, Prof. A.R. Darji "To Study the Effect of Silica Fume on Properties of Macro Polypropylene Blended Fiber Reinforced Concrete" IJSRD - International Journal for Scientific Research & Development| Vol. 2, Issue 09, 2014.
27. Khayat, K.H., Aitcin, P.C., (1993). "Silica fume: a unique supplementary cementitious material". In: Ghosh, S.N. (ed.) Mineral Admixtures in Cement and Concrete, vol. 4. Pp 227-265.
28. EFFECT OF SILICA FUME ON VARIOUS PROPERTIES OF FIBRE REINFORCED CONCRETE by Rahul Dogra International Journal of Civil Engineering and Technology (IJCIET) Volume 7, Issue 4, July-August 2016
29. Neel Shah, Prof. A.R. Darji "To Study the Effect of Silica Fume on Properties of Macro Polypropylene Blended Fiber Reinforced Concrete" IJSRD - International Journal for Scientific Research & Development| Vol. 2, Issue 09, 2014
30. H.J.H, Hüsken G. and Quercia G. "Research on use of nano silica"
31. Bentur, A., Mindess S., and Skalny, J., 1989, „Reinforcement of normal and high strength concrete with fibrillated polypropylene“, fiber reinforced cements and concretes recent developments edited by R.N.Swamy, ISBN 1-18166-415-7, pp.229-239.